

## Research Article

## Synthesis and Mechanical Characterization of Grewia Serrulata Short Natural Fiber Composites

Mahesh G T<sup>Å\*</sup>, Satish Shenoy B<sup>Å</sup>, Padmaraj N H<sup>Å</sup> and Chethan K N<sup>Å</sup>

<sup>Å</sup>Dept of Automobile Engineering, Manipal Institute of Technology Manipal, Karanataka, India-576104

Accepted 9 January 2014, Available online 01 February 2014, **Special Issue-2, (February 2014)**

### Abstract

*Composite materials based on Grewia Serrulata as reinforcing fibers and polyester resin were prepared by hand lay-up technique and characterized, in terms of mechanical performance. Optimizing the length of the fibers for adequate mechanical properties is attempted in the present work. The mechanical properties of the composites were improved by reinforcing with short fibers. These scarcely cited fibers in the contemporary research work assure confidence for the further enhancement in their usage for various applications with continued research. The low density of the fibers results in light weight composites so that the overall weight of the system could be reduced considerably.*

**Keywords:** *Grewia Serrulata, Natural fiber, Tensile Strength, Flexural Strength, Composite*

### 1. Introduction

Rapidly depleting fossil fuel sources have triggered the urgent need for the development of alternative and nature friendly materials such as natural fiber composites. Currently, synthetic fibers like glass, carbon and aramid are widely being used in polymer-based composites because of their high stiffness and strength properties. However, these fibers have serious drawbacks in terms of their lack of biodegradability, higher initial processing costs, recyclability, energy consumption, machine abrasion, health hazards, etc. (Rout *et al*, 2001), (Bledzki *et al*, 1999). As an alternative to these synthetic materials, the use of natural fibers in making newer materials for variety of applications is gaining popularity. Some of the proven fields of applications for such materials are automotive, packaging, furniture and interiors. This is because of multiple advantages associated such as biodegradability, lightweight materials, non-allergic nature, less reliance on rapidly depleting petroleum resources etc. (Abdelmouleh *et al*, 2007), (Tserki *et al*, 2005). In this context, any new or alternative method that reduces the burden on the expensive fuels is a well come effort.

A bast fiber from the plant Grewia Serrulata which has not been found used in making the materials is tried in the present work as the reinforcement. It is presumed that by utilizing such fibers for the composites, value addition can be done for such plant products. Traditionally Grewia Serrulata fibers have been used by local people for making ropes, knots, bags, threads, baskets etc. But presently, we have used these fibers as reinforcement in composite materials. It generally contains cellulose, hemicelluloses

and lignin in the ranges of 58–62%; 20–25% and 15-20% respectively.

In the current study, polymer matrix composites, with Grewia Serrulata as reinforcement and polyester as the resin, are prepared and characterized. The density of the fibers used in the study is estimated as 1.1 g/cc and that of the polyester resin is 1.02 g/cc.

Some of the researches carried out by using natural fibers as reinforcements is taken as a basis for the present work. These are summarized below.

(Hamdan *et al*, 2008) carried out study on the effect of alkaline treatment on tensile properties of sugar palm fiber reinforced epoxy composite. The sugar palm epoxy composite plate was fabricated on one type volume fraction i.e. 10%. The laminated composite plate was produced by hand lay-up process and was cut to form a specimen test based on ASTM D638-99.

(Mulinari *et al*, 2011) studied mechanical properties of coconut fibers Reinforced Polyester Composites. Coconut fibers were extracted and dried at 80°C for 24 h. Polyester was used as a resin along with treated coconut fiber. Composite was manufactured by compression moulding technique. Mechanical tests were carried through in a servo-hydraulic MTS model 810.23M. The dimensions were according to ASTM standards D3039.

(Hung *et al*, 2008) conducted a study on tensile behaviors of the coir fiber and related composites after alkali treatment. Coconut fibers were obtained from retting process. Coir fibers were treated in the NaOH solutions at the room temperature (26–28 °C) with densities of 2%, 4%, 6%, 8% and 10%, respectively. Alkali treated and untreated were cured in an oven, and then conditioned under the environment of relative humidity of 65% and

\*Corresponding author: Mahesh G T

temperature at 20°C for 24 h before the tensile strength test.

(Rajulu *et al*, 2005) reinforced short natural fiber belonging to the species *Hildegardia Populifolia* in styrenated polyester matrix. The mechanical properties of the composites reinforced with alkali treated fibers were determined and compared with untreated fibers. Tensile modulus is measured using Instron UTM model: 1175 (UK). Alkali treatment of the fibers enhanced the tensile modulus by 3.5% and compressive strength by 7.5%.

(Shinji *et al*, 2008) studied the mechanical properties of kenaf fibers. Kenaf fiber with a diameter of 50–150 micrometer and length of 500 mm were used. An emulsion-type poly-lactic acid resin was used as the matrix. Tensile tests and three-point flexural tests were conducted. Tensile tests were performed at a strain rate of 0.02 per min and a gauge length of 50 mm. Unidirectional biodegradable composites fabricated using an emulsion-type poly-lactic acid resin and kenaf fibers at a fiber content of 70% have high tensile and flexural strengths of 223 MPa and 254 MPa, respectively.

The literature review reveals that natural fibers can be reinforced with suitable polymers and can be used for light load carrying and in automotive interior applications. In this paper authors studied the mechanical properties of *Grewia Serrulata* fibers reinforced with polyester resins.

## 2. Preparation of composites

The fibres selected for the preparation of the composites were extracted from *Grewia Serrulata* plant which belongs to Tiliaceae family, locally known as Gurguri.

The stems from the plant were collected and immersed in water for four days. After soaking fibres were extracted from the stem by using metal wire brush without damaging them. The fibre strands which were originally in lumps were split manually and made into single strands. The fibres were split into single strands without damaging the fibre surface. Then they were cut into sizes of 10 mm, 20 mm and 30mm. The fibres were dried in room temperature for 48 hours to reduce the moisture content.

Hand lay-up technique is used for the fabrication of the natural fibre - polyester composites. The specimens were prepared in a mould having dimensions 30 × 15 × 0.5 cm. Specimens were prepared with 10mm, 20mm and 30mm length of fibres keeping volume fraction of fibres as 15%. The prepared specimens were allowed to cure in room temperature for 36 hours. Figure 1 and 2 shows the mould used to prepare the specimen and *Grewia Serrulata* fibre reinforced composite material respectively.



**Fig.1** Mould for specimen preparation



**Fig.2** *Grewia Serrulata* reinforced composite

## 3. Mechanical Properties Investigation

The specimens of *Grewia Serrulata* natural fibre reinforced with polyester resin tested for mechanical properties such as tensile strength, flexural strength and wear test according to ASTM standards. Tensile test of specimens carried out according to ASTM D 3039 at a feed rate 0.5mm/min in universal testing machine Instron 3366. Figure 3 shows the specimen used to prepare the composite material.



**Fig.3** Specimen for Tensile Strength

Three point flexural strength of the *Grewia Serrulata* fibre reinforced composite materials was investigated according to ASTM D 790. Figure 4 shows the specimen used to conduct flexural strength test.



**Fig.4** Specimen for flexural strength test

Wear can be considered as erosion from its derivative and original position on a solid surface performed by the action of the surface. It can also be defined as a process where interaction between two surfaces and bounding faces solids within the working environment results in dimensional loss of one solid with or without loss of material.

Pin on disk wear test rig is used for the study of wear pattern of the test specimens. In this test a pin slides on a horizontally- oriented rotating disk. Sliding speed is controlled by rotational speed and sliding path diameter. Contact pressures are controlled by applied load and pin diameter. A stationary block specimen is pressed with a constant force against a rotating ring specimen at 90° to the ring's axis of rotation. Friction between the sliding surfaces of the block and ring results in loss of material from both pieces. Figure 5 shows the setup used to

determine the tensile strength, flexural strength and wear rate of different length fibre reinforced composite material.



Fig.5 Tensile, Flexural and Wear test setup

4. Result and discussions

In the present study tensile test on 10mm, 20mm and 30mm length Grewia Serrulata natural fiber composites was carried out. Figure 6 shows the load vs extension curve of tensile test. From the figure it is clear that as the length of fibers decreased it leads to improvement in the tensile strength. The increase in tensile strength with short fiber reinforcement is due to enhanced load transfer between matrix and fiber interface. However composite showed a decline in tensile strength beyond optimum fiber length of 10mm due to agglomeration of fibers.

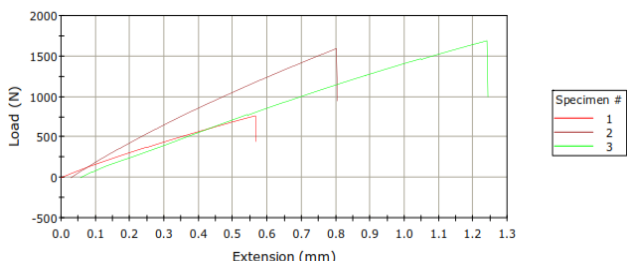


Fig.6 Load vs Extension curve of tensile strength

Table 1 show the maximum load applied on the specimen before breaking point.

Table.1 Tensile test results of specimen

Specimen	Maximum Load in N	Tensile strength at maximum load (MPa)	Modulus (MPa)
1	763.635	10.909	2084.162
2	1592.48	22.749	3255.12
3	1690.46	24.149	2040.57

Flexural strength test of specimens shows that the specimens prepared with 20mm length fiber composites could bear higher load than the other specimens. Table 2 shows the values of maximum flexural stress and strain for the different length of fiber reinforcements. Figure 7 shows the plot of flexural stress vs flexural strain.

Table.2 Results of flexural strength test

Specimen	Flexural load at maximum stress(N)	Maximum flexural stress (MPa)
1	32.38	5.60
2	261.59	45.20
3	121.53	21.00

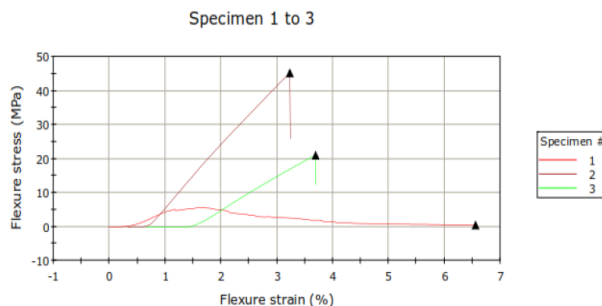


Fig.7 Plot of Flexural stress vs flexural strain

It is found from the results of the wear test that short reinforcement fibers in the composite showed least wear characteristics at all rotational speeds of the disc. Also, in general as the relative speed between the disc and the composite increases the wear rate increases as well. Maximum wear rate was observed with 20 mm length reinforced fibers while 10 mm length fibers offered least wear at all speeds of rotation of the disc. This is probably due to proper mixing and wetting of the fibers in the mixture. The wear rate of specimens with 10, 20 and 30 mm length reinforcing fibers is shown in table 3.

Table 3: Results of wear test

Fibre length in Specimen	Speed (RPM)	Weight before wear in grams	Weight after wear in grams	Difference in gram	Volume removed in mm <sup>3</sup>	Sliding distance in mm	Wear rate mm <sup>3</sup> /mm
10mm	200	0.742	0.741	0.001	0.918	848230.016	1.082
		0.741	0.740	0.001	0.918	848230.016	1.082
		0.740	0.739	0.001	0.918	848230.016	1.082
	400	0.922	0.920	0.002	1.836	1130973.355	1.623
		0.920	0.919	0.001	0.918	1130973.355	0.811
		0.919	0.917	0.002	1.836	1130973.355	1.623
	600	0.917	0.915	0.002	1.836	1696460.033	1.623
		0.915	0.912	0.003	2.755	1696460.033	1.623
		0.912	0.909	0.003	2.755	1696460.033	1.623
20mm	200	1.114	1.112	0.002	1.836	1266345.024	1.450
		1.112	1.110	0.002	1.836	1266345.024	1.450
		1.110	1.108	0.002	1.836	1266345.024	1.450
	400	1.164	1.162	0.002	1.836	1130973.355	1.623
		1.162	1.160	0.002	1.836	1130973.355	1.623
		1.160	1.158	0.002	1.836	1130973.355	1.623
	600	1.060	1.057	0.003	2.755	1696460.033	1.623
		1.057	1.054	0.003	2.755	1696460.033	1.623
		1.054	1.050	0.004	3.673	1696460.033	2.165
30mm	200	1.122	1.121	0.001	0.918	848230.016	1.082
		1.121	1.120	0.001	0.918	848230.016	1.082
		1.120	1.119	0.001	0.918	848230.016	1.082
	400	1.261	1.259	0.002	1.836	1130973.355	1.623
		1.259	1.257	0.002	1.836	1130973.355	1.623
		1.257	1.255	0.002	1.836	1130973.355	1.623
	600	1.188	1.185	0.003	2.755	1696460.033	1.623
		1.185	1.183	0.003	2.755	1696460.033	1.623
		1.183	1.180	0.003	2.755	1696460.033	1.623

Conclusions

- 1) Grewia Serrulata plant fibres can be successfully used as reinforcements in the preparation of composite materials.
- 2) Tensile strength of the composites with a fibre length of 10 mm is higher than for composites with longer fibres as reinforcement.
- 3) Flexural strength of composites with 20mm length fibres is optimum, thus too short or too longer fibres as reinforcement offers lower bending properties.
- 4) The 10 mm fibre length composite has the least wear rate, thus short fibre composites can be used in applications such as in making the parts with slight relative motion between them.

**References**

- Rout J, Misra M, Tripathy S, Nayak SK, Mohanty A K, (2001), The influence of fiber treatment on the performance of coir-polyester composites, *Composite Science Technology*; 61(9):1303–10.
- Bledzki AK, Gassan J, (1999), Composites reinforced with cellulose based fibers, *Polymer Science*, 24(2):221–74.
- Abdelmouleh M, Boufis S, Belgacem MN, Dufresne, (2007), Short natural-fibre reinforced polyethylene and natural rubber composites: effect of silane coupling agents and fibre loading, *Composite Science Technoogyl 2007*, 67 (7–8):1627–39.
- Tserki V, Zafeiropoulos NE, Simon F, Panayiotou C, (2005), A study of the effect of acetylation and propionylation surface treatments on natural fibres, *Composites Part A – Applied Science Manufacturing* 2005, 36(8):1110–8.
- M.M. Hamdan D, Bachtiar, S.M. Sapuan, M.M. Hamdan, (2008), The effect of alkaline treatment on tensile properties of sugar palm fiber reinforced epoxy composites, *Materials and Design* 28 November 2007 1285–1290.
- Mulinari, D.R. Baptista, Souza, J. V. C., Voorwald, H.J.C, (2011), Mechanical Properties of Coconut Fibers Reinforced Polyester, *Procedia Engineering* 10 2074–2079
- Huang Gu, (2008), Tensile behaviours of some high performance filaments after NaOH treatment, *Materials and Design* 29 1893–1896
- Varada Rajulu A, Babu Rao G and Ganga Devi L, (2005), Mechanical Properties of Short, Natural Fiber Hildegardia populifolia-reinforced Styrenated Polyester Composites, *Journal of Reinforced Plastics and Composites*, Vol. 24, No. 4
- Shinji Ochi,(2008), Mechanical properties of kenaf fibers and kenaf/PLA composites, *Mechanics of Materials* 40 446–452